

DESCO INDUSTRIES INCORPORATED

3651 WALNUT AVENUE, CHINO CA 91710
 PHONE (909) 627-8178 | WEB DescoIndustries.com

QUALIFICATION REPORT – ANSI/ESD S20.20

DESCO SLIP RESISTANT CONDUCTIVE DISPOSABLE BOOTIE

ANSI/ESD S20.20	DESCO Test Results	Test Methods
-----------------	--------------------	--------------

Point-to-Groundable-Point Resistance (ohms), 48-72 hours, 10V/100V, N=6 specimens

@12%RH, 23°C	$< 1.0 \times 10^9$	See Table 1	ANSI/ESD SP9.2
@ 50%RH, 23°C	$< 1.0 \times 10^9$	See Table 1	ANSI/ESD SP9.2

Test Equipment (Calibration records and test results are located at our corporate lab (Sanford, NC)):

For Test Method ANSI/ESD SP9.2:


- ETS Controlled Environment Chamber (Model 5532)
- SCS Surface Resistance Meter (Model 770761)

Test Data:

Table 1 – Resistance (ohms)

Specimen	Point-to-Groundable-Point Resistance (ohms)	
	@ 23°C, 12%RH, 48-72 hours	@ 23°C, 50%RH, 48-72 hours
1	3.75×10^6	1.36×10^7
2	6.15×10^6	1.59×10^7
3	9.15×10^6	4.94×10^6
4	6.57×10^6	1.31×10^7
5	9.60×10^6	8.03×10^6
6	3.32×10^6	1.75×10^7
Min =	3.32×10^6	4.94×10^6
Max =	9.60×10^6	1.75×10^7
Mean =	6.42×10^6	1.22×10^7

References:

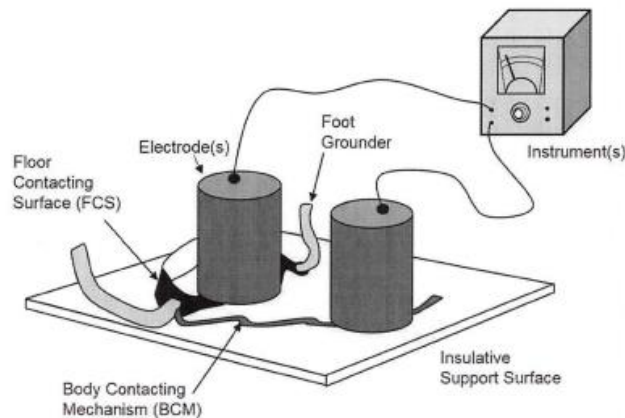

ANSI/ESD SP9.2 – Figure 1: Foot Grounder Resistance Test